

## Extra machinability modeling

### Modeliranje povečane obdelovalnosti

MIHA KOVAČIČ<sup>1,2,\*</sup>, MATEJ PŠENIČNIK<sup>2</sup>

<sup>1</sup>ŠTORE STEEL, d. o. o., Štore, Slovenia

<sup>2</sup>University of Nova Gorica, Laboratory for Multiphase Processes, Nova Gorica, Slovenia

\*Corresponding author. E-mail: Miha.Kovacic@store-steel.si

**Received:** December 17, 2008

**Accepted:** June 06, 2009

**Abstract:** The steels with extra machinability are made according to special technological process. It depends on several parameters, particularly on the steel chemical composition, whether the steel will meet the criterion of extra machinability. By special test it is established whether the steel has extra machinability or not. In our researches the prediction of machinability of steels, depending on input parameters, was performed by logistic regression and genetic programming. The research shows that genetic programming model performs better. The best model developed during the simulated evolution was practically verified.

**Izveček:** Jekla s povečano obdelovalnostjo so izdelana s posebnim tehnološkim postopkom. Povečana obdelovalnost jekla je odvisna od mnogih parametrov, predvsem pa od kemične sestave. Obdelovalnost jekla se določa na podlagi posebnega preizkusa. V naši raziskavi smo za napovedovanje obdelovalnosti jekla uporabili logistično regresijo in genetsko programiranje. Rezultati kažejo, da se bolje obnese metoda genetskega programiranja. Rezultati modela so bili preizkušeni v praksi.

**Key words:** steel, extra machinability, modeling, logistic regression, genetic programming

**Ključne besede:** jeklo, povečana obdelovalnost, modeliranje, logistična regresija, genetsko programiranje

## INTRODUCTION

In general, tool steels are divided into ordinary steels and steels with extra machinability. These two groups differ in the technology of steel manufacture, which influences the steel properties during machining processes (e. g. turning, milling). In case of steel with extra machinability it is possible to reach much higher resistance of cutting tools even with higher cutting speeds, therefore the price of such steels is 10 % higher on the average than the price of the ordinary steel.<sup>[1]</sup>

The steels with improved machinability retain all good qualities of ordinary steels their advantage being that they allow machining at 25–50 % higher cutting speeds, 4–6 times lower tool wear and 30 % reduction of machining cost.<sup>[1]</sup>

In case of steel with extra machinability the molten metal is treated with calcium, which improves their machining properties. Instead of aluminium oxides the steel with extra machinability contains calcium aluminates of 2–20  $\mu\text{m}$  size which are of regular forms and uniformly scattered. In this steel the calcium aluminates have sulphide surface. The heat in the cutting zone softens the sulphide surface and ensures the cutting tool to have lubrication effect. As a result, the tool

wear in lower and higher machining speeds are allowed.<sup>[1]</sup>

The test of the steel machinability is performed according to the technological standard ISO 3685.<sup>[2]</sup> The test process is demanding and time-consuming. As long as the data on machinability are not known, the steel cannot be included in the further technological process. If the steel does not reach the degree of extra machinability it is considered to be ordinary steel. The steel machinability is influenced particularly by the chemical composition. As there are several chemical elements in the steel its machinability is hard anticipate and predict. In addition, also other technological parameters change, which additionally make the steel machinability prediction difficult.

In the paper prediction of steel machinability by logistic regression and genetic programming was used. The both methods were also compared. Prediction of machinability of steel helps to avoid time-consuming and expensive testing of steel machinability and to contribute to improvement of the material flow in the production process.

## TEST OF TOOL RESISTANCE

Appropriateness of steel with extra machinability is verified by parameter  $v_{15}$

which is prescribed for each grade of steel.

The parameter  $v_{15}$  is the speed of cutting of the tool which is worn out within 15 min. The tool wear is prescribed. The test of tool resistance is performed on a CNC lathe.

That test is carried out for each batch. The batch is the quantity of steel cast as a whole in the steelworks. The mass of one batch is 52 000 kg. Each batch is identified by its identification number. The steel sample for finding out the machinability must have the diameter of at least 60 mm and the minimum length of 500 mm. After machining (turning) without cooling, within time  $t$  (approximately fifteen minutes) and with selected speeds, the wear of the cutting insert is measured under a microscope (Figure 1). The tip of the insert ( $V_{BB}$ ) may be worn out for not more than 0.30 mm and the entire insert edge ( $V_{BB \max}$ ) for not more than 0.60 mm. Afterwards, the parameter  $v_{15}$  is calculated by Taylor's equation:<sup>[3]</sup>

$$v \cdot t^n = C \quad (1)$$

where  $v$  is cutting speed,  $t$  is cutting time,  $n$  is constant depending on tool material (insert). Constant  $n$  for ceramic inserts is 0.25.

With cutting speed  $v = 330$  m/min and

time  $t = 22.6$  min, within which tool wear takes place,  $v_{15}$  amounts to:

$$v \cdot t^n = v_{15} \cdot 15^n \quad (2)$$

$$v \cdot t^{0.25} = v_{15} \cdot 15^{0.25}$$

$$v_{15} = v \cdot \frac{t^{0.25}}{15^{0.25}}$$

$$v_{15} = 330 \cdot \frac{22.6^{0.25}}{15^{0.25}} = 365.6 \text{ m/min}$$

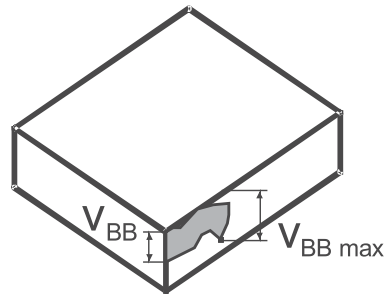


Figure 1. Side wear of the insert

## EXPERIMENTAL BACKGROUND

The data were collected in the period of 13 months in the factory Štore Steel Ltd. from Slovenia. The most influencing parameters are the sample diameters and the chemical elements (calcium, oxygen and sulphur) necessary for production of steel with extra machinability. 146 batches were made. Out of them 125 were adequate. If the batch is adequate this means when parameter  $v_{15}$  in the individual batch exceeds the prescribed value  $v_{15}$  for that batch.

The prescribed value of parameter  $v_{15} = 85.61\%$ . The number of each steel grade specimens and the average chemical composition and prescribed  $v_{15}$  for steel grade is presented in Table 1.

**Table 1.** The number of each steel grade specimens and average chemical composition and prescribed  $v_{15}$

Steel grade	Number of specimens	w(Ca)/%	w(O)/%	w(S)/%	$v_{15}$ /(m/min)
16MnCrS5	2	0.0305	0.034	0.0275	410
C45	139	0.0293	0.0462	0.0270	360
C50	2	0.0235	0.0145	0.021	360
C15	1	0.029	0.019	0.028	450
St70.2	2	0.03	0.0375	0.029	360

The experimental data and extra machinability suitability are presented in Table 2. If the batch of steel is adequate then it is marked with logical variable 1 and with 0, if it is not.

**Table 2.** The experimental data

#	Batch number	Steel grade	Sample diameter	w(Ca)/%	w(O)/%	w(S)/%	$v_{15}$	Prescribed $v_{15}$	Extra machinability
1	36968	C45	19.0	0.024	0.019	0.031	327	360	0
2	37101	16MnCrS5	60.0	0.026	0.044	0.027	453	410	1
3	37236	C50	70.0	0.026	0.005	0.022	308	360	0
4	37237	C50	70.0	0.021	0.024	0.02	346	360	0
...	...	...	...	...	...	...	...	...	...
143	37322	C45	70.0	0.027	0.018	0.025	261	250	1
144	37358	C45	70.0	0.033	0.042	0.028	452	450	1
145	37359	C45	70.0	0.029	0.044	0.022	459	450	1
146	37360	C45	68.0	0.033	0.046	0.025	438	410	1

### EXTRA MACHINABILITY MODELING

Evaluation of models were determined by Bayesian analysis (true positive  $TP$ , true negative  $TN$ , false positive  $FP$ , false negative  $FN$ ) applying sensitivity  $SENS = TP/(TP+FN)$ , specificity  $SPEC = TN/(FP+TN)$ , positive predictive value  $PPV = TP/(TP+FP)$  and negative predictive value  $NPV = TN/(FN+TN)$ .

The higher are values of mentioned parameters the better model fits to experimental data.

The parameters in the mathematical models for extra machinability are denoted as:

- $\varphi$  - sample diameter
- $w(\text{Ca})/\%$  - mass fraction of calcium
- $w(\text{O})/\%$  - mass fraction of oxygen
- $w(\text{S})/\%$  - mass fraction of sulphur

### Logistic regression modeling

The most important results of logistic regression are presented in Table 3.

According to the logistic regression results the logistic mathematical model for extra machinability is:

$$\lg\left(\frac{p}{1-p}\right) = 0.058 \cdot \varphi + 123.607 \cdot w(\text{Ca}) + 101.616 \cdot w(\text{O}) + 326.759 \cdot w(\text{S}) - 18.537 \quad (3)$$

where  $p$  is the probability of steel not being extra machinability steel. If the probability  $p$  was lower than 0.5, then the extra machinability was denoted as 1 otherwise as 0.

The logistic regression model sensibility is 0.976, specificity 0.524, positive predictive value 0.924, negative predictive value 0.786 and test efficiency 0.911.

### Genetic programming modeling

Genetic programming is probably the most general evolutionary optimization method.<sup>[4-6]</sup> The organisms that undergo adaptation are in fact math-

**Table 3.** Logistic regression results

Parameter	B	S. E.	Wald	df	Sig.	Exp(B)
$\varphi$	0.058	0.032	3.278	1	0.070	1.060
$w(\text{Ca})/\%$	123.607	67.251	3.378	1	0.066	4.805
$w(\text{O})/\%$	101.616	27.171	13.986	1	0.000	1.353
$w(\text{S})/\%$	326.759	131.147	6.208	1	0.013	8.123
Constant	-18.537	5.089	13.268	1	0.000	0.000

emathical expressions (models) for extra machinability prediction consisting of the available function genes (i.e., basic arithmetical functions) and terminal genes (i.e., independent input parameters, and random floating-point constants). In our case the models consist of: function genes of addition (+), subtraction (-), multiplication (\*) and division (/), terminal genes of sample diameter ( $\varphi$ ) and chemical composition of steel (Ca, O and S).

Random computer programs of various forms and lengths are generated by means of selected genes at the beginning of simulated evolution. Afterwards, the varying of computer programs during several iterations, known as generations, by means of genetic operations is performed. After completion of varying of computer programs a new

generation is obtained that is evaluated and compared with the experimental data, too.

The result values of models for extra machinability prediction above zero predicted that the steel is extra machinability steel (value 1), otherwise not (value 0).

The process of changing and evaluating of organisms is repeated until the termination criterion of the process is fulfilled. This was the prescribed maximum number of generations.

For the process of simulated evolutions the following evolutionary parameters were selected: size of population of organisms 500, the greatest number of generation 100, reproduction probability 0.4, crossover probability 0.6,

$$\begin{aligned}
 & 2w(O) - \frac{0.89395 \cdot w(O)}{\frac{1.70735}{w(O)} + w(O) + \frac{2.32712}{w(S)}} + w(S) - \tag{4} \\
 & 0.89395 \left( w(O) - \frac{0.89395w(O)}{\frac{-1.70735}{w(O)} + \frac{1.16356}{w(S)}} + w(S) \right) \\
 & \frac{w(O)(w(Ca) + \varphi + w(S)) - \frac{0.48069 \left[ -\frac{1.70735}{w(O)} + w(O) + \frac{2.32712}{w(O) + w(S)} \right]}{-2.32712 + w(O)}}{w(O) + \frac{0.89395(w(O) + w(S))}{2.32712}} \\
 & \frac{w(O)(w(Ca) + \varphi + 3w(S)) + \frac{2.32712}{- \varphi + w(O) - w(S)} - \frac{1.11863 \left[ -\frac{1.70735}{w(O)} + w(O) + \frac{2.32712}{w(O) + w(S)} \right]}{- \varphi + w(O) - w(S)}}{w(O)(2.32712 + w(S))}
 \end{aligned}$$

the greatest permissible depth in creation of population 6, the greatest permissible depth after the operation of crossover of two organisms 10 and the smallest permissible depth of organisms in generating new organisms 2. Genetic operations of reproduction and crossover were used. For selection of organisms the tournament method with tournament size 7 was used.

We have developed 100 independent civilizations of mathematical models for prediction of extra machinability. Only one out of 100 is presented in eq. 4 (page 343)

With sensibility of 1, specificity 0.810, positive predictive value 0.969, negative predictive value 1 and test efficiency 0.973.

## CONCLUSIONS

Due to their specific properties if compared with ordinary steels, the steels with extra machinability will represent a growing share on the market. Their advantage over the remaining steels, in particular, is that they can be machined at higher machining speeds and that they assure smaller cutting tool wear.

In researches two approaches were used for predicting the steel machinability – logistic regression and genetic

programming. Evaluation of models was determined by Bayesian analysis.

The logistic regression model was obtained with sensibility 0.976, specificity 0.524, positive predictive value 0.924, negative predictive value 0.786 and test efficiency 0.911.

The best genetic programming model (out of 100) performed better with sensibility of 1, specificity 0.810, positive predictive value 0.969, negative predictive value 1 and test efficiency 0.973. Out of 146 values the best model wrongly predicts 4 values; it means that its reliability is 97.26 %. In case of all 4 wrong predictions the model predicts that the steel has appropriate machinability, while in fact it does not have it.

Research has shown that by using the genetic programming method for prediction of appropriateness of the steel machinability it is possible to establish efficient planning and optimizing of production, to reduce the costs of researches and the handling changes and, finally, to increase satisfaction of the buyers due to shorter delivery times.

The future researches will be focused on testing the mathematical model and optimizing the chemical composition. The prognosis is optimistic.

## REFERENCES

- [1] [www.store-steel.si](http://www.store-steel.si) (2009).
- [2] ISO 3685:1993, Ed. 2, Tool-life testing with single-point turning tools.
- [3] GALANTE, G., LOMBARDO, A., PASSANANTI A., Tool-life modeling as a stochastic process, *International journal of machine tools and manufacture*, 1998, 38, 1361–1369.
- [4] KOVAČIČ, M., BREZOČNIK, M., TURK, R. (2005): Modeling of hot yield stress curves for carbon silicion steel by genetic programming. *Materials and manufacturing processes*, Vol. 20, 1–10.
- [5] KOVAČIČ, M., URATNIK, P., BREZOČNIK, M., TURK, R. (2007): Prediction of the bending capability of rolled metal sheet by genetic programming. *Materials and manufacturing processes*, Vol. 22, 634–640.
- [6] KOZA, J. R. (1999): Genetic programming III. *Morgan Kaufmann*, San Francisco, 1154 p.